

ecore™

Commercial
Flooring



ECOfit Field Lamination Rolls

INSTALLATION AND MAINTENANCE MANUAL

Manufactured in the U.S.A. by:

ecore

Revised on 01/17/2018
Supersedes all previous versions.
Check website for updates.

Table of Contents

INSTALLATION	3-9
Job Site Conditions	3
Subfloors	3
Subfloor Preparation	3-4
Storage & Handling	5
Installation of Underlayment Pad	5-6
Skim Coating Underlayment	6
Installation Finished Flooring	7-9
MAINTENANCE	10-18
Specifier Information	10
Cleaning Procedures	11-12
ECOGuard Procedures	13-18
WARRANTY	19
Warranty	19

INSTALLATION

I. JOB SITE CONDITIONS

- A. Installation should not begin until after all other trades are finished in the area. If the job requires other trades to work in the area after the installation of the floor, the flooring should be protected with an appropriate cover.
- B. Areas to receive flooring should be weather tight and maintained at a minimum uniform temperature of 65° F (18° C) for 48 hours prior to, during, and after installation.

II. SUBFLOORS

- A. ECOfit rolls may be installed over concrete, approved Portland based self-leveling materials, and wood. Gypsum based patching and leveling compounds are not acceptable.
- B. Wood Subfloors: Wood subfloors should be double construction with a minimum thickness of 1". The floor must be rigid, free from movement, and have at least 18" of well-ventilated air space below.
- C. Underlayments: The preferred underlayment panel is APA underlayment grade plywood, minimum thickness of 1/4", with a fully sanded face.

Note: Particle board, chip board, Masonite, and lauan are not considered suitable underlayments.

- D. Concrete Floors: Concrete shall have a minimum compressive strength of 3000 psi. It must be fully cured and permanently dry.

III. SUBFLOOR REQUIREMENTS AND PREPARATION

- A. Subfloor shall be dry, clean, smooth, level, and structurally sound. It should be free of dust, solvent, paint, wax, oil, grease, asphalt, sealers, curing and hardening compounds, alkaline salts, old adhesive residue, and other extraneous materials, according to ASTM F710.
- B. Subfloor should be smooth to prevent irregularities, roughness, or other defects from telegraphing through the new flooring. The surface should be flat to the equivalent of 3/16" (4.8 mm) in 10 feet (3.0 m).
- C. Mechanically remove all traces of old adhesives, paint, or other debris by scraping, sanding, or scarifying the substrate. Do not use solvents. All high spots shall be ground level and low spots filled with an approved cementitious based patching compound.
- D. All saw cuts (control joints), cracks, indentations, and other non-moving joints in the concrete must be filled with an approved cementitious based patching compound.
- E. Expansion joints in the concrete are designed to allow for expansion and contraction of the concrete. If a floor covering is installed over an expansion joint, it more than likely will fail in that area. Expansion joint covers designed for resilient floor coverings should be used.
- F. Always allow patching materials to dry thoroughly and install according to the manufacturer's instructions. Excessive moisture in patching material may cause bonding problems or a bubbling reaction with the E-Grip III™ adhesive.

INSTALLATION

HAZARDS:

SILICA WARNING - Concrete, floor patching compounds, toppings, and leveling compounds can contain free crystalline silica. Respirable crystalline silica (particles 1-10 micrometers) can be produced by cutting, sawing, grinding, or drilling. Respirable silica is classified by OSHA as an IA carcinogen and is known to cause silicosis and other respiratory diseases. Avoid actions that cause dust to become airborne. Use local or general ventilation, or protective equipment, to reduce exposure below applicable exposure limits.

ASBESTOS WARNING - Resilient flooring, backing, lining felt, paint, or asphaltic “cutback” adhesives can contain asbestos fibers. Avoid actions that cause dust to become airborne. Do not sand, dry sweep, dry scrape, drill, saw, beadblast, or mechanically chip or pulverize. Regulations may require that the material be tested to determine asbestos content. Consult the documents titled, “Recommended Work Practices for Removal of Existing Resilient Floor Coverings,” available from the Resilient Floor Covering Institute.

LEAD WARNING - Certain paints can contain lead. Exposure to excessive amounts of lead dust presents a health hazard. Refer to applicable federal, state, and local laws and the publication, “Lead Based Paint: Guidelines for Hazard Identification and Abatement in Public and Indian Housing,” available from the United States Department of Housing and Urban Development.

- G. Moisture must be measured using the RH Relative Humidity test method per ASTM F2170 standard. Moisture content should not exceed 85% RH. If the levels exceed the limitations, the installation should not proceed until the situation has been corrected.
- H. In the event that a moisture mitigation system is required, it must conform to the ASTM F3010 Standard Practice for Two-Component Resin Based Membrane Forming Moisture Mitigation Systems for use Under Resilient Floor Coverings.
- I. It is essential that pH tests be taken on all concrete floors. If the pH is greater than 9, it must be neutralized prior to beginning the installation.
- J. Adhesive bond tests should be conducted in several locations throughout the area. Glue down 3’ x 3’ test pieces of the flooring with the recommended adhesive and trowel. Allow to set for 72 hours before attempting to remove. A sufficient amount of force should be required to remove the flooring and, when removed, there should be adhesive residue on the subfloor and on the back of the test pieces.
- K. It is essential that pH tests be taken on all concrete floors. If the pH is greater than 9, it must be neutralized prior to beginning the installation.
- L. Adhesive bond tests should be conducted in several locations throughout the area. Glue down 3’ x 3’ pieces of the flooring with the recommended adhesive and trowel. Allow to set for 72 hours before attempting to remove. A sufficient amount of force should be required to remove the flooring, and there should be adhesive on the subfloor and the back of the flooring.

INSTALLATION

IV. Material Storage and Handling

- A. Material should be delivered to the job site in its original unopened packaging with all labels intact.
- B. Roll material should always be stored lying down. Storing rubber on end will curl the edges, resulting in permanent memory of the material. Do not store rolls higher than 4 rolls or for more than 6 months.
- C. All edges with memory curl should be straight cut before installation. In some instances it may be necessary to weigh down the seam until adhesive develops a firm set.
- D. Inspect all material for visual defects prior to beginning the installation. No labor claim will be honored on material installed with visual defects. Verify the material delivered is the correct style, color, and amount. Any discrepancies must be reported immediately before beginning installation.
- E. The material and adhesive must be acclimated at room temperature for a minimum of 48 hours before starting installation.

NOTE: ECOsurfaces flooring is manufactured from recycled materials and slight variance in shade and color chip dispersion is normal. It is the installer's responsibility to inspect all products to ensure the correct style, thickness, and color. Any moderate to severe discrepancies should be reported immediately before beginning installation.

V. Installation of the Field Laminated ECOfit Underlayment Pad - Step 1

- A. Begin by dry-laying rolls to allow product to relax for a minimum of two hours. Roll material is stretched slightly when it is rolled at the factory. At the job site the installer should allow all rolls to relax for a minimum of two hours before cutting to fit.

NOTE: ECOfit underlayment will be laid perpendicular to the direction of the finished flooring material.



INSTALLATION

- B. After all above procedures are performed, begin application of Ecore's E-Grip III one-component, zero-VOC urethane adhesive. Apply E-Grip III to the substrate using recommended 1/16" square notch trowel. Take care not to spread more E-Grip III than can be covered by flooring and rolled within 30 minutes. The open time of the adhesive is 30–40 minutes at 70° F and 50% relative humidity.

NOTE: The open time of adhesive is affected by temperature and humidity. High temperatures and high humidity will cause the adhesive to set-up quickly. Low temperatures and low humidity will cause adhesive to cure at a slower rate. The installer should monitor on-site conditions and adjust open time accordingly.

- C. Carefully lay the material into the wet adhesive. Do not let the material drop as this will cause air to be trapped beneath the flooring.
- D. Continue this process for each consecutive drop. Work at a pace so that you are always folding material back into wet adhesive. Do not allow E-Grip III to cure on your hands or the flooring. Immediately wipe off excess adhesive with a rag dampened with mineral spirits. Cured adhesive is very difficult to remove. We strongly suggest wearing gloves when using E-Grip III.
- E. Immediately roll the floor with a 75-100 lb. roller to ensure proper transfer of adhesive. Overlap each pass of the roller by 50% of the previous pass to ensure that the floor is properly rolled. Roll the width first, then the length. Re-roll again after 30–45 minutes.
- F. Hand roll all seams after the entire floor has been rolled. If some seams are gapping, hold them together temporarily with masking tape. Do not use duct tape as it may leave a residue on the floor. Remove tape after adhesive has developed a firm set.
- G. Keep foot traffic off the floor for a minimum of 24 hours. Foot traffic and rolling loads can be detrimental to the installation, causing permanent indentations or bubbles in the uncured adhesive.

VI. Installation of the ECOfit Underlayment Pad Skim Coating - Step 2

After completion of step 1 and allowing the adhesive to cure for 24 hours, you can begin step 2.

- A. Using a flat trowel, apply E-Grip III at a rate of 80–100 sq. ft. per gallon over entire ECOfit underlayment pad. This will leave a seamless appearance and create one large monolithic layer in which to install the finished flooring. Adhesive layer should be as thin as possible.
- B. Allow skim coat to dry approximately six hours before proceeding with dry-lay of finished flooring. You may begin installation of the finished flooring when the adhesive is not tacky to the touch.



INSTALLATION

VII. Installation of the ECOfit Finished floor surface - Step 3

- A. All ECOsurfaces rolls must be unrolled and installed in the same direction (directional arrows are stamped on bottom of the rolls). Rolls are labeled with batch numbers and roll numbers. Do not mix batch numbers together and install all rolls in consecutive order. See Diagram 1.

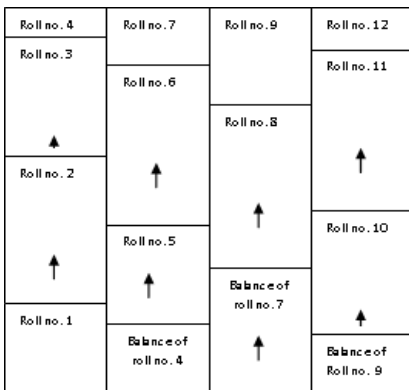


Diagram 1

- B. Roll material is stretched slightly when it is rolled at the factory. At the job site the installer should allow all rolls to relax for a minimum of two hours before cutting to length and width.
- C. Cut the first sheet at the required length including enough to run up the wall and overlap for seaming at each end.
- D. Position the first sheet against the wall and square with the room.
- E. Cut second sheet with proper extra length.
- F. Position second sheet of 3.2mm material with a 2" overlap over the first roll at the seam for 48" wide rolls, and 5" overlap for 51" wide rolls.
- G. Repeat for each consecutive sheet necessary to complete the area or those rolls that will be installed that day.

SEAMING METHODS

3.2mm thick material: Double cut by placing a 4" wide scrap of material under the seam area. Using a straight edge and new razor blade, hold the knife straight up and down and cut through both pieces in one cut.



INSTALLATION

VIII. Installation of the ECOfit Finished floor Adhesive Application - Step 4

- A. After all above procedures are performed, begin application of E-Grip III Ecore's recommended one-component, Zero VOC polyurethane adhesive. Apply E-Grip III to the underlayment pad using a 1/16" x 1/32" x 5/64" U-notch trowel.
- B. Spread adhesive using proper notched trowel. Take care not to spread more E-Grip III than can be covered by flooring within 30 minutes. The open time of the adhesive is 30–40 minutes at 70° F and 50% relative humidity.

NOTE: The open time of adhesive is affected by temperature and humidity. High temperatures and high humidity will cause the adhesive to set-up quickly. Low temperatures and low humidity will cause adhesive to cure at a slower rate. The installer should monitor on-site conditions and adjust open time accordingly.



Diagram 2

- C. Fold over second half of first roll and half of second sheet. Spread adhesive. At seam area spread adhesive at 90 degrees to seam to eliminate excessive adhesive oozing up at seam. Roll material. See Diagram 2.
- D. Carefully lay the material into the wet adhesive. DO NOT let the material drop because this will cause air to be trapped beneath the flooring.
- E. Continue the process for each consecutive drop. Work at a pace so that you are always folding material back into wet adhesive.

NOTE: Never leave adhesive ridges or puddles, they will telegraph through the material. **Do not allow E-Grip III to cure on your hands or the flooring.** Immediately wipe off excess adhesive with a rag dampened with mineral spirits. Cured adhesive is very difficult to remove. We strongly suggest wearing gloves when using E-Grip III.

- F. Immediately roll the floor with a 75-100 lb. roller to ensure proper transfer of adhesive. Overlap each pass of the roller by 50% of the previous pass to ensure that the floor is properly rolled. Roll the width first then the length. Re-roll again after 30-45 minutes.

INSTALLATION

- G. Hand roll all seams after the entire floor has been rolled. If some seams are gapping, hold them together temporarily with masking tape. Do not use duct tape as it will leave a residue on the floor. Remove tape after adhesive has developed initial set, approximately 2 hours.
- H. It may be necessary to weigh down the seam until the adhesive sets. Boxes of cove base work well. Cover the entire seam. If some seams are gapping, hold them together temporarily with masking tape or blue painter's tape. Do not use duct tape as it will leave a residue on the floor. Remove tape after adhesive has developed initial set, approximately 2 hours.
- I. Keep foot traffic off the floor for a minimum of 24 hours. Keep rolling loads off floor for a minimum of 72 hours. Foot traffic and rolling loads can cause permanent indentations or adhesive failure.



SPECIFIER INFORMATION

Important Information for the Specifier

Ecore recommends our Environmentally Friendly Maintenance Products and Procedures for ECOfit.

Proper protection and maintenance of ECOfit post-installation should be specified by the architect/designer. ECOfit products should not be subject to construction debris and potential damage caused from heavy duty construction activities.

FLOOR PROTECTION

The specifier should include specification details to protect the floor post-installation and until job construction is complete, such as covering the entire floor with paper or another floor covering device (plastic, plywood, etc.) until construction is completed and thorough cleaning and maintenance can be implemented.

ASSIGNMENT OF CLEANING AND MAINTENANCE

The specifier should determine and assign the responsibility for the initial cleaning and finishing. This responsibility should be specifically assigned to the flooring contractor, general contractor, maintenance contractor, or owner.

MAINTENANCE

Cleaning Procedures & Maintenance- ECOfit with ECOguard

Maintenance

Steps	Green Products	Dilute	Diluted Coverage	Pads & Brushes
Initial Cleaning	Ecore’s E-Cleaner	10 oz/gal water	2,000 sq ft/gal	Soft nylon brush, or approved pad
Finishing	Ecore’s E-Finish	None	1,500 sq ft/gal	Soft nylon brush or microfiber mop
ECOguard Finishing	(see ECOguard section for detailed instructions)			
Daily Cleaning	Ecore’s E-Cleaner	2-4 oz/gal water	6,000 sq ft/gal	Soft nylon brush or microfiber mop
Heavy Soil and Restorative Cleaning	Ecore’s E-Strip	16 oz/gal water	1,200 sq ft/gal	Brown pad or black pad
Stripping	E-Strip	16 oz/gal water	1,200 sq ft/gal	Brown pad or black pad

ECORE CLEANING AND FINISHING PROGRAM

A. Initial Cleaning

1. Remove all surface soil, debris, sand, and grit by sweeping, dust mopping, or vacuuming.
 - a. Scrub floor with Ecore’s recommended E-Cleaner, using buffer or auto scrubber with an approved pad or soft nylon brush.
2. Pick up solution with a wet vacuum, rinse with clean water, and allow to dry thoroughly (6-8 hours).

B. Initial Floor Finish Application

1. Finish options:
2. Ecore’s E-Finish for a low satin finish. Apply 2-3 thin coats of finish. Work finish into flooring with a soft nylon brush and let it thoroughly dry between coats.
3. Provide sufficient cure time of final coat before allowing foot traffic (at least 2 hours).

C. Daily/Regular Cleaning

1. Sweep, dust mop or vacuum floor to remove surface soil, debris, sand, and grit.
2. Damp mop with a microfiber mop or auto-scrub with a soft nylon brush or microfiber mop using Ecore’s approved E-Cleaner low foam cleaner.

MAINTENANCE

Note: FLOORS TREATED WITH E-Finish - When cleaning floors finished with E-Finish use only a microfiber mop and nylon brush. Pads will remove finish on floors treated with E-Finish.

D. Restorative Maintenance

Stripping the finish is not needed until there is noticeable accumulation of dirt and contaminants embedded in the finish. Normally this accumulation occurs in hard to reach and high traffic areas. Following a good maintenance program and applying thin coats of finish when the look calls for it and only where it is needed will result in little finish build-up, increasing the time between stripping.

1. Sweep or vacuum to remove loose soil.
2. Heavy scrub using a rotary scrubber or automatic scrubber with a black or brown pad and stripper solution Ecore’s E-Strip.
3. Pick up solution with wet vac.
4. Rinse with clean water.
5. Allow floor to thoroughly dry.
6. Apply floor finish following initial finish application instructions.

E. Heavy Soil

1. Hard-to-clean and greasy areas may require a higher concentration of Ecore’s E-Cleaner.

IMPORTANT MAINTENANCE TIPS

- Use high CFM vacuum to pick up dust.
- Wait for floor to dry thoroughly before applying floor finishes, usually 24 hours.
- Apply only thin coats of floor finishes with finish mop. Buffing finish into the floor with a soft nylon brush is beneficial.

Note: If area is too small for a buffer or auto scrubber, a nylon deck brush may be used to remove scuff marks or heavy soil. Brush should be approximately 22 gauge.

ECOGuard is considered a permanent sealer and not intended to be stripped from the rubber as a standard procedure. This procedure is for restorative maintenance purposes only.

Approved Cleaning / Stripping Pads

Manufacturer	Cleaning	Stripping-Contact ECORE Tech Services
3 M	White 4100, Beige 4200	Black 7200, Brown 7100, Blue 5300
Taski	White	Black, Purple
ECOLAB	White	Black

MAINTENANCE

ECOGuard Clear Coat Sealer Instruction Manual

Description

ECOGuard is a water based, clear polyurethane maintenance coat. ECOGuard is formulated for interior applications and offers excellent environmental resistance to abrasion and impact, while offering an attractive matte finish.

Tools / Materials Required

Safety Glasses
Latex or Rubber Gloves
21" paint tray or rectangular mop bucket for sealer
Applicator Trim Pads
Automatic Buffer
Safety / utility knife
Trash bags
18" stir sticks
Drill
Rags
Microfiber Mop
Microfiber Mop Cover
Paint mixer paddle

MAINTENANCE

Surface Preparation

- An improperly prepared surface can act as a bond breaker and result in a project failure. It is important to remove all dirt, grease, wax, oil, paint or other contaminants before applying the ECOguard. ECOguard can be applied over the existing factory applied finish after all construction debris and soil have been removed from the surface.

Precautionary Measures

- Suggested to allow ECOguard to cure for 48 hours before cleaning.
- Suggested to allow ECOguard to cure for 48 hours before rolling chairs and dollies.
- Suggested to allow ECOguard to cure for 24 hours before introducing foot traffic.
- If traffic and/or rolling loads need to be introduced earlier than listed above, the surface should then be protected with an appropriate plywood or Luan.
- Remove ECOguard spills and drips immediately from other surfaces before dry.
- Suggested not to re-use microfiber pads after applying ECOguard.
- Seal floor in one step rather than in sections for best results.
- If sealer dries on microfiber pad, replace with new microfiber pad for best results.
- Sealer will obtain full strength in 5-7 days. Care should be taken during the first 5-7 days to prevent damage to the coating. Extra coats will extend the curing cycle.
- Do not use string mops or other unapproved applicators to apply ECOguard. The use of unapproved mops may result in a poor application of the sealer and complete removal may be required.
- Work from one side of the room to the other using a scrubbing motion with microfiber mop keeping a wet edge.

Application Methods

1. Application of ECOguard Over Uncoated EcoSurfaces
2. Application Over Existing New ECOguard Factory Applied Sealer
3. Surface Preparation and Re-Application of ECOguard Sealer
4. Removal , Stripping “Complete Removal” of ECOguard Sealer
5. Cleaning and Maintenance Instructions

1. Application Of ECOguard Over Uncoated ECOsurfaces

- **IMPORTANT! Stir the ECOguard thoroughly before application to ensure consistent sheen.** Stir sealer for 3-5 minutes or until all sediment at bottom of pail is mixed in.
- Safety glasses should be worn when mixing, pouring or applying ECOguard.
- Apply first coating of ECOguard to the rubber surface using Ecore’s recommended Microfiber Mop. An applicator trim pad may be used for areas around the perimeter.
- Additional one to two coats are recommended and an ample amount of time is required between coats. Allow each coat to dry thoroughly to touch before applying the next coat, about 2 - 4 hours.

MAINTENANCE

- Over unfinished rubber the coverage rate is approximately 400-500 sq ft per gallon. Second and Third coat coverage approximately 600-800 sq ft per gallon.
- Apply ECOguard when surface temperature is 65 degrees Fahrenheit or higher and maintained for 72 hours before and after installation.
- Wear rubber or latex gloves when applying the ECOguard. Sealer will not harm the skin but is difficult to remove once it dries. Wash hands immediately after contact with ECOguard with soap and water.
- Allow ECOguard to cure for 48 hours before cleaning the surface.

2. Application Over Existing ECOguard Factory Applied Sealer

- **Factory coated product should not require additional field coats. Should an additional coat be requested, one should suffice.**
- **IMPORTANT! Stir the ECOguard thoroughly before application to ensure consistent sheen.** Stir sealer for 3-5 minutes or until all sediment at bottom of pail is mixed in.
- Safety glasses should be worn when mixing, pouring or applying ECOguard.
- Wear rubber or latex gloves when applying the ECOguard. Sealer will not harm the skin, but is difficult to remove once it dries. Wash hands immediately after contact with ECOguard with soap and water.
- Apply ECOguard when surface temperature is 65 degrees Fahrenheit or higher and maintained for 72 hours before and after installation.
- Apply one coating of ECOguard to the rubber surface using Ecore's recommended Microfiber Mop. An applicator trim pad may be used for areas around the perimeter.
- Additional coats are acceptable and an ample amount of time is required between coats. Allow each coat to dry thoroughly before applying the next coat, about 2-4 hours.
- Coverage rate is approximately 600-800 sq. ft. per gallon over previously coated surfaces.
- Allow ECOguard to cure for 48 hours before cleaning the surface.

3. Surface Preparation and Re-Application of ECOguard Sealer

- An improperly prepared surface can act as a bond breaker and result in a project failure. It is important to remove all dirt, grease, wax, oil, paint or other contaminants before re-applying the ECOguard. ECOguard can be applied over the existing factory applied finish after all construction debris and soil have been removed from the surface.
- It is recommended to clean the surface thoroughly with a buffer or auto scrubber using a 3M red or aqua pad. Keep in mind that these pads will slightly abrade the finish and continued use will remove the sealer. Cleaning with these pads will slightly abrade the finish creating an acceptable surface to apply the new finish coat.
- **NOTE:** Manufacturers make different pads of different texture in like colors. It is recommended to contact Ecore's Technical Service Department for guidance in pad selection.
- **Stir the ECOguard thoroughly before application to ensure consistent sheen.**
- Apply one coating of ECOguard to the rubber surface using Ecore's recommended Microfiber mop. An applicator trim pad or 4" roller may be used for areas around the perimeter.

MAINTENANCE

- Additional coats are acceptable and an ample amount of time is required between coats. Allow each coat to dry thoroughly before applying the next coat, about 2-4 hours.
- Coverage rate is approximately 600-800 sq. ft. per gallon over previously coated surfaces.
- Apply ECOguard when surface temperature is 65 deg Fahrenheit or higher and maintained for 72 hours before and after installation.
- Safety glasses should be worn when mixing, pouring or applying ECOguard.
- Wear rubber or latex gloves when applying the ECOguard. Sealer will not harm the skin but is difficult to remove once it dries. Wash hands with soap and water after contact.
- Allow ECOguard to cure for 48 hours before cleaning the surface.

4. Removal / Stripping ECOguard Sealer

- ECOguard is difficult to completely remove from the surface of the rubber and may take several attempts. ECOguard is removed by abrasion using an approved stripping pad. Anything used to chemically remove the sealer will jeopardize the integrity of the rubber.
- To remove, use E-Strip 42 oz. per gallon water and a buffer fitted with a black or brown stripping pad. Manufacturers make different pads of different texture in like colors. **It is recommended to contact Ecore’s Technical Service Department for guidance in pad selection.**
- Apply a liberal amount of diluted stripper to the surface of the rubber and work buffer from one side to the other until sealer is removed. Successfully removing the sealer will be dependent on undulations in the substrate and may take several passes with the buffer or auto scrubber.

- **CAUTION – A “standard” black pad** should be the most aggressive pad used. **The use of a high performance black pad such as 3M’s 7300 series is NOT RECOMMENDED and will act as a sander and will damage the surface of the rubber.** Ecore assumes no liability in the event of damage to the rubber in the removal process. ECOguard is considered a permanent sealer and not intended to be stripped from the rubber as a standard procedure. This procedure is for restorative maintenance purposes only. To re-apply ECOguard please follow step 1.

Maintenance Instructions

Steps	Green Products	Dilute	Tools
Initial Cleaning	Ecore’s E-Cleaner	10 oz / Gal Water	Soft Nylon Brush or Microfiber Mop
Daily/Weekly Cleaning	Ecore’s E-Cleaner	2-4 oz / Gal Water	Soft Nylon Brush or Microfiber Mop
Heavy Soil	Ecore’s E-Strip	10 oz / Gal Water	Soft Nylon Brush or approved pad

MAINTENANCE

ECOSurfaces Coated with ECOguard

A. Initial Cleaning

NOTE: Sealer should have 48 hours minimum to cure before introducing moisture.

1. Remove all surface soil, debris, sand, and grit by sweeping or vacuuming.
2. Scrub floor with Ecore’s recommended E-Cleaner, using a buffer or auto scrubber with a soft nylon brush. We recommend a 175 RPM buffer or auto scrubber. If soil is minimal, a microfiber mop may be used.
3. Pick up remaining residue with a wet vac and damp mop floor. Allow floor to dry.

B. Daily/Weekly Cleaning

1. Remove all surface soil, debris, sand, and grit by sweeping or vacuuming.
2. Damp mop or scrub floor using Ecore’s recommended E-Cleaner or equivalent with a soft nylon brush or microfiber mop. For heavier scuff marks, a more aggressive pad may be used. **Please contact Ecore’s Technical Department for guidelines on pad selection.**
3. Clean remaining residue from floor with a wet vac and damp mop floor. Allow floor to dry thoroughly before introducing foot traffic.

C. Heavy Soil Cleaning

1. Remove all surface soil, debris, sand, and grit by sweeping or vacuuming.
2. Scrub floor using Ecore’s recommended E-Cleaner with a soft nylon brush or more aggressive recommended pad. **Contact Ecore’s Technical Department for aid in pad selection.** "Follow Dilution Schedule" above.
3. Pick up remaining residue with a wet vac and damp mop floor. Allow floor to dry.

Note: If area is too small for a buffer or auto scrubber, a nylon deck brush may be used to remove scuff marks or heavy soil. Brush should be approximately 22 gauge.

Approved Cleaning / Stripping Pads

Manufacturer	Cleaning	Stripping
3 M	White 4100, Beige 4200	Black 7200, Brown 7100, Blue 5300
Taski	White	Black, Purple
ECOLAB	White	Black

MAINTENANCE

Recommended Tools / Materials



paint tray



Microfiber Mop



21"

Microfiber Mop Cover



Rectangular Mop Bucket



Applicator Trim Pad



Applicator Trim Pad



Mixing Paddle



Safety Glasses



Safety Knife



Latex Gloves



Shop Towels



Rags

WARRANTY

All Ecore rubber flooring is guaranteed to be free from manufacturing defects on both material and workmanship. If such a defect is discovered, the customer must notify Ecore either through the contracting installer, distributor, or directly. If found to be defective within five years under normal non-abusive conditions, the sole remedy against the seller will be the replacement or repair of the defective goods, or at the seller's option, credit may be issued not exceeding the selling price of the defective goods.

ECOsurfaces warranty shall not cover dissatisfaction due to improper installation, damage from improper maintenance or usage, or general misuse, including and without limitation: burns, cuts, tears, scratches, scuffs, damage from rolling loads, damage from cleaning products not recommended by Ecore, slight shade variations or shade variations due to exposure to direct sunlight, or differences in color between samples or photographs and actual flooring.

Excluded from Warranty

These warranties do not apply to the following:

1. The exact matching of shade, color, or mottling.
2. Any express or implied promise made by any salesman or representative.
3. Tears, burns, cuts, or damage due to improper installation, improper use, or improper cleaning agents or maintenance methods.
4. Wear from chairs or other furniture without proper floor protectors will void the warranty. Care should be taken to protect the flooring from damage by using good quality protective feet for chairs, tables, and other furniture. Chair mats may be required under chairs with casters/wheels.
5. Labor costs for installation of original or replacement material.
6. Sale of "Seconds," "Off Goods," or other irregular (non-first-quality) flooring materials. With respect to "Seconds" or "Off Goods," such are sold "as is," and ECOsurfaces makes no warranties whatsoever, express or implied with respect thereto, including warranties of merchantability or fitness for a particular purpose.
7. Problems caused by moisture, hydrostatic pressure, or alkali in the sub-floor.
8. Problems caused by uses, maintenance, and installation that are contrary to ECOsurfaces specifications, recommendations or instructions.
9. Material installed with obvious defects.
10. Damage to flooring products from high heels or spike heels.
11. Damage to flooring products from rubber mats or rubber backed mats.
12. Installation of ECOsurfaces products with adhesives other than those recommended by ECOsurfaces.
13. Fading and/or discoloration resulting from heavy sunlight penetration and ultraviolet ray exposure from direct or glass-filtered sunlight.
14. Material that is not installed and maintained as recommended by ECOsurfaces.
15. Damage to flooring products from pallet jack and tow-motor traffic.
16. Environments where the product will be exposed to animal fats, vegetable oils, grease or petroleum based materials. (i.e.: commercial kitchens or auto repair facilities.)
17. Premature wear and deterioration from spikes and skate blade exposure.
18. Differences in color between products and photography.
19. Embossing/density deviations between product and samples, photography.

These warranties are in lieu of any other warranty expressed or implied. ECOsurfaces shall not be liable for any incidental or consequential damages which may result from a defect. Some states do not allow the exclusion or limitation of incidental or consequential damages, so the above limitation or exclusion may not apply to you. These warranties give you specific rights, and you may also have rights which may vary from state to state. To know what your legal rights are in your state, consult your local or state Consumer Affairs Office or your State Attorney General. For complete and latest warranty information for products within the ECOsurfaces collection, please visit www.ecorecommercialflooring.com.



119 South Tree Drive – Lancaster, PA 17603
800-258-08431 – www.ecorecommercialflooring.com

Manufactured in the U.S.A. by:

The ecore logo, consisting of the word "ecore" in a bold, blue, lowercase, sans-serif font.

715 Fountain Ave – Lancaster, PA 17601

©2015 All designs and colors are copyrighted by Ecore Intl.
ECOsurfaces is a registered trademark of Ecore Intl.